


# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 3/1/95	3. REPORT TYPE AND DATES COVERED Final Report 6/91 - 12/94	
4. TITLE AND SUBTITLE Intelligent Synthetic Polymers			5. FUNDING NUMBERS DAAL03-91-G-0169	
6. AUTHOR(S) P. D. Calvert H. K. Hall Jr.				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Arizona Tucson, AZ 85721			8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U. S. Army Research Office P. O. Box 12211 Research Triangle Park, NC 27709-2211			10. SPONSORING/MONITORING AGENCY REPORT NUMBER  ARO 28900-13-MS	
11. SUPPLEMENTARY NOTES The view, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT  Approved for public release; distribution unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  Block copolymers of hydrophobic and hydrophilic acrylates were to be made and tested for control of mineralization by calcium oxalate. Acrylate copolymers in solution inhibited crystal growth to an extent dependent on their acid content but not dependent on the architecture. Solid films of acrylate polymers became mineralized when exposed to oxalate solutions. This effect was very dependent on the structure of the polymer. Methods were also developed for forming inorganic layers on polymer films by overlaying two polymers, each containing solubilized precipitants. Reaction and precipitation would occur at the film/film interface.  Cross-linked methacrylic acid films could be templated with rigid molecules such as caffeine, and then would be absorb the templated molecule selectively from solution. Methods were also developed for coupling short protein chains to acrylate polymers as a route to combining biochemical specificity with localization on inorganic surfaces.				
14. SUBJECT TERMS  Group Transfer Polymerization, Block Copolymers, Biomineralization, Selective Membranes			15. NUMBER OF PAGES 8	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT  UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE  UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT  UNCLASSIFIED	20. LIMITATION OF ABSTRACT  UL	

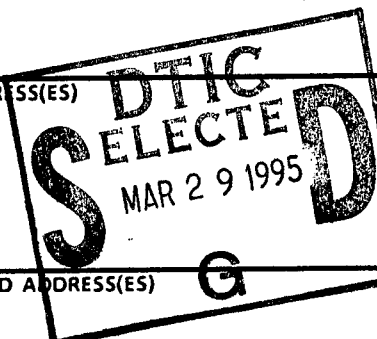

19950327 166

## GENERAL INSTRUCTIONS FOR COMPLETING SF 298

The Report Documentation Page (RDP) is used in announcing and cataloging reports. It is important that this information be consistent with the rest of the report, particularly the cover and title page. Instructions for filling in each block of the form follow. It is important to *stay within the lines* to meet optical scanning requirements.

**Block 1. Agency Use Only (Leave blank).**

**Block 2. Report Date.** Full publication date including day, month, and year, if available (e.g. 1 Jan 88). Must cite at least the year.

**Block 3. Type of Report and Dates Covered.** State whether report is interim, final, etc. If applicable, enter inclusive report dates (e.g. 10 Jun 87 - 30 Jun 88).

**Block 4. Title and Subtitle.** A title is taken from the part of the report that provides the most meaningful and complete information. When a report is prepared in more than one volume, repeat the primary title, add volume number, and include subtitle for the specific volume. On classified documents enter the title classification in parentheses.

**Block 5. Funding Numbers.** To include contract and grant numbers; may include program element number(s), project number(s), task number(s), and work unit number(s). Use the following labels:

C - Contract	PR - Project
G - Grant	TA - Task
PE - Program Element	WU - Work Unit Accession No.

**Block 6. Author(s).** Name(s) of person(s) responsible for writing the report, performing the research, or credited with the content of the report. If editor or compiler, this should follow the name(s).

**Block 7. Performing Organization Name(s) and Address(es).** Self-explanatory.

**Block 8. Performing Organization Report Number.** Enter the unique alphanumeric report number(s) assigned by the organization performing the report.

**Block 9. Sponsoring/Monitoring Agency Name(s) and Address(es).** Self-explanatory.

**Block 10. Sponsoring/Monitoring Agency Report Number.** (If known)

**Block 11. Supplementary Notes.** Enter information not included elsewhere such as: Prepared in cooperation with...; Trans. of...; To be published in.... When a report is revised, include a statement whether the new report supersedes or supplements the older report.

**Block 12a. Distribution/Availability Statement.** Denotes public availability or limitations. Cite any availability to the public. Enter additional limitations or special markings in all capitals (e.g. NOFORN, REL, ITAR).

**DOD** - See DoDD 5230.24, "Distribution Statements on Technical Documents."

**DOE** - See authorities.

**NASA** - See Handbook NHB 2200.2.

**NTIS** - Leave blank.

**Block 12b. Distribution Code.**

**DOD** - Leave blank.

**DOE** - Enter DOE distribution categories from the Standard Distribution for Unclassified Scientific and Technical Reports.

**NASA** - Leave blank.

**NTIS** - Leave blank.

**Block 13. Abstract.** Include a brief (*Maximum 200 words*) factual summary of the most significant information contained in the report.

**Block 14. Subject Terms.** Keywords or phrases identifying major subjects in the report.

**Block 15. Number of Pages.** Enter the total number of pages.

**Block 16. Price Code.** Enter appropriate price code (*NTIS only*).

**Blocks 17. - 19. Security Classifications.** Self-explanatory. Enter U.S. Security Classification in accordance with U.S. Security Regulations (i.e., UNCLASSIFIED). If form contains classified information, stamp classification on the top and bottom of the page.

**Block 20. Limitation of Abstract.** This block must be completed to assign a limitation to the abstract. Enter either UL (unlimited) or SAR (same as report). An entry in this block is necessary if the abstract is to be limited. If blank, the abstract is assumed to be unlimited.

INTELLIGENT SYNTHETIC POLYMERS:  
Final report to the Army Research Office

P.I.'s: Paul Calvert, Materials Science and Engineering, and H.K. Hall Jr, Chemistry,  
University of Arizona

Grant Number: DAAL03-91-G-0169 1991-1994

FOREWORD

The work described here is step on the journey to a synthetic world which is at least as subtle, varied and versatile as the natural world. Here we have exploited new methods of polymerization allow us to control polymer structure and produce molecules that are a little like proteins. This control of polymer architecture should let us mimic biomineralization, biological transport processes and ultimately biological catalysis. Before we can do this we not only have to have the polymerization methods but we have to understand the design rules.

We would like to thank David Kaplan of the U.S. Army laboratories in Natick for his help in setting up this project and for useful discussions throughout the last three years.

Accession For	
NTIS	CRA&I <input checked="" type="checkbox"/>
DTIC	TAB <input type="checkbox"/>
Unannounced <input type="checkbox"/>	
Justification .....	
By .....	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

# INTELLIGENT SYNTHETIC POLYMERS

## BACKGROUND

Proteins are distinguished from synthetic polymers by their synthesis from a nucleic acid template which gives rise to a chain with an absolutely specified sequence of amino acids. Synthetic polymer chains are limited to simple repeats of a single unit, random copolymers or two or more units or blocks of two types of unit. This has not limited our ability to produce polymers with mechanical properties similar to those of structural proteins such as collagen or keratin. However it is not clear that we can make synthetic enzymes or transport proteins without detailed control of the chain sequence.

New methods for block polymerization of acrylic polymers give us more flexibility. Group Transfer Polymerization (GTP), developed by Sogah at DuPont, and anionic polymerization of acrylates, developed by Teyssie in Liege, both allow a wide range of acrylate monomers to be block copolymerized. This still only allows simple sequences of two or three blocks to be made but it does give access to a wide range of possible chain units, analogous to the variety of acidic, basic, polar and non-polar amino acids. Thus we still cannot approach the complexity of proteins but this is definitely a step forward.

We can now explore what special properties can be built into polymers using these blocks with controlled functionality. The work done under this grant built on two earlier projects. In one, which was motivated by a concern with ceramic processing, a series of block copolymers of acrylates were made by Group Transfer Polymerization (GTP) and tested as dispersants for alumina particles in solvents (1). GTP is a newly developed polymerization method which allows block copolymers to be made from polar monomers. This gives us the ability to make polymer chains where some sections interact strongly with inorganic surfaces while other sections are soluble in non-polar solvents.

A second area of previous work concerned the growth on inorganic particles in polymers. This research was stimulated by a desire to duplicate the composite structure of bone where the reinforcing hydroxyapatite grows within the tough collagen matrix. We had formed composites with inorganic oxides formed from soluble alkoxides by an in situ reaction in the polymer. One aim of the new project was to extend this to crystalline precipitates such as calcium carbonate and hydroxyapatite.

## GOALS OF THIS PROJECT

Biomineralization and membrane transport were selected as two phenomena where the controlling effects of proteins were more likely to be due to the architecture of hydrophilic and hydrophobic blocks than to local site geometry. Block copolymers of hydrophobic and hydrophilic acrylates were to be made and tested. Methods were also to be developed for coupling short protein chains to acrylate polymers. The protein part of the hybrid molecule would then give the specificity while the acrylate could be used to anchor the chain.

## RESULTS

### Biomimetic Mineralization

There is general agreement that biological mineralization depends on close control of the inorganic precipitation by the organic phase. This results in control of particle size, shape and alignment which must be responsible for the good mechanical properties of mineralized tissues. There is less agreement on the mechanism of this control. Initially it was thought that mineralizing proteins carried anionic carboxylate or phosphate groups with a spacing that matches that of the metal ions in one crystal face of the mineral. The metal ions bind to the protein with the correct spacing to nucleate a crystal. There has been shown to be a close match between the spacing of ions along a protein chain in the  $\beta$ -sheet structure and the calcium ions in one face of aragonite. However the protein structure does not seem to vary with the mineral being formed and the lattice match is limited to one direction.

A second theory is that the local geometry of negative charge centers in the anionic groups corresponds to the geometry of the anions in the crystal. As a result, polymer-bound cations are as exposed as the ions in a growing crystal surface and this promotes binding of free anions in the right conformation. Other factors which have been suggested to be important include binding and orientation of preformed nuclei, catalytic activity of the surface which forms local high concentrations of cations or anions or favorable nucleation conditions within the polymer surface rather than actually at the interface.

The work on the modification of calcium salt precipitation by block co-polyacrylates was carried out by Mualla Oner, a postdoctoral fellow and has been fully reported (2, 3). Calcium oxalate was selected as the precipitating system since there are fewer potentially confusing side-issues than with calcium carbonate and calcium phosphates. Butylmethacrylate-methacrylic acid copolymers were added in various proportions, in the ppm range, to a crystallizing solution of calcium oxalate. The effect of the copolymers on crystallization time was measured. We had anticipated that a critical number of acid groups in a sequence would be necessary to inhibit crystallization. In fact the main effect seen depended on the fraction of acid groups in the chain but not on the sequence of them.

Beyond this we produced a series of polymer gels and films to study their mineralization tendency in solution. The ideal is to deposit, on a substrate, a film which promotes crystal growth. Thus a metastable supersaturated solution will grow crystals in or on the film but not free in solution. This has been put forward by Mann as the key to biomineralization (4). We have found that some hydroxylated acrylate polymers will mineralize from a calcium oxalate solution (presented at the Materials Research Soc. Fall 1994). Rieke has similarly treated surfaces with self-assembled monolayers for mineralization by cadmium sulfide and iron oxide (5). While we can form mineral films on organic surfaces, we do not fully understand why. It is clear that Mann's original concept of lattice templating is wrong and that the important interactions are more at the level of individual ion binding.

Fully developed systems of this type could become the basis for a technology for device manufacture. Patterned films would mineralize locally with materials that are too temperature sensitive to withstand the conditions of silicon technology and give rise to a family of devices with better chemical and thermal sensitivity, closer to the biological senses.

### Protein-Polymer Hybrids

Work has continued to develop methods for coupling anionically polymerized acrylates to polypeptides. This was taken to the point of coupling alanine ethyl ester to the end of polybutylacrylate. This is chemically interesting but alanine has no very interesting functions. Masataka Kubo has extended this work to coupling histidine to the end of the acrylate chain, with protection of the ring secondary amine (6). The chain makes the histidine soluble in a range of organic solvents. This polymer should have interesting properties as an interfacially-active binder of metal ions. We have 100 mg of the material for testing. Kubo also made acrylate chains with a phosphoserine end group which mimics the phosphorylated proteins involved in shell mineralization.

Sajiv Boggavarapu is studying membrane interactions with various organic compounds as part of a parallel ASSERT project. When he has reached the required level of competence, he will incorporate the histidine polymer into an acrylate film and test for copper binding on the surface and in the film. In addition he will carry out oxalate crystallization over surfaces of acrylates containing the coupled phosphoserine to monitor its effect as a nucleator.

The synthetic work has shown that acrylates can be polymerized anionically to form a narrow molecular weight distribution and coupled to simple peptides. This gives us hydrophilic or hydrophobic chains of quite uniform length with a peptide end group. For a simple amino acid or peptide, it is necessary to protect the acid end group when coupling the amino end to the acrylate. In the case of histidine it is necessary to protect both the acid function of the amino acid and the ring  $>NH$  group. There are two difficulties in extending this to a large arbitrary peptide. Firstly, all side chain  $>NH$  and  $-COOH$  must be protected. This can be done by artificial protein synthesis, given a supply of amino acids with protected side groups. Secondly, the reaction rate of the acrylate chain with the peptide chain will decrease rapidly as both chain lengths increase.

Given the above, we do have a general method to couple short synthetic peptides to acrylate chains of defined length.

### Templating Membranes

This work is being carried out under the associated AASERT project. It has been known for some time that a cross-linked gel of methacrylic acid can be "templated" selectively to take up a molecule with multiple hydrogen-bonding sites, such as caffeine. Templating is achieved by carrying out the original polymerization in the presence of caffeine which is then extracted by a solvent treatment. It is believed that the resin bonds around the template so that a hole with the correct geometry remains after the template molecule is removed. This effect has only been demonstrated with bulk resin which is

granulated and tested by chromatography. The template molecule is more likely to attach to the resin and so passes more slowly through a chromatography column than do other similar molecules. This effect is a bit mysterious in that one would expect that, given sufficient mobility to allow the template molecules to diffuse out, the gel would rearrange on a molecular scale during the extraction.

Sajiv Boggavarapu has developed a method for templating films. This depends on using trimethoxysilylpropylmethacrylate to cross-link the imprinted gels by a hydrolytic reaction after film formation. Using spectroscopic studies of these films, we have compared absorption of theophylline and caffeine by templated films. Selectivity for the templating molecule by about a factor of two is seen, caffeine-templated films take up more caffeine than theophylline and vice versa. Controls on un-templated films are in progress.

This effect has considerable implications for selective detection and removal of organic compounds. We are planning to extend the work to templating cavities for crystal growth.

#### Polymer bilayer methods for patterned mineralization

One route to localize deposits of minerals in a polymer is to identify specific surface groupings that will promote mineralization from a solution. This has only proved to be possible if the solution conditions are very closely controlled. An effort by Calvert, carried out at Sandia National Labs (presented MRS meeting, Boston, Fall 1994), assessed different methods of putting one reagent into a polymer film reservoir and then reacting with a solution to cause precipitation. A most reliable method was to incorporate one reagent, such as cadmium salts, into a polymer film which was printed onto a substrate. This film was overprinted with a second polymer containing a second reagent, such as a sulfide source. On heating a film of cadmium sulfide grew at the interface. The second polymer was then removed by a selective solvent. This method offers a route to the controlled and patterned deposition of multiple layer devices using sequential printing steps and liquid treatments.

This moves us toward the goal of developing a family of VLSI techniques that could be used under ambient conditions with aqueous solutions and would let us incorporate multiple layers of sensitive organic and biological molecules into devices.

#### Future Work

Solid Freeform Fabrication (SFF) allows the deposition of a wide variety of materials to build functional parts. Our system comprises computer-driven syringes which deposit slurries, of particles dispersed in liquid monomers, in patterns under the control of a CAD program. As each layer is formed it is cured to a solid. Simultaneous deposition of several materials allows complex composites to be formed. This method has much in common with biological growth of materials in that composite parts can be formed layer by layer. Chemical synthesis of shapes becomes possible from reagents being diffused into each layer. The localized control of the process is similar in scale to cellular control and allows composition and properties to be varied on the 100  $\mu\text{m}$  scale

throughout the part.

Bone, tooth and shell also deposit in a layerwise fashion. We have come to see that SFF methods will allow formation of synthetic mineralized materials. Previously we had not seen how to avoid the problem of large shrinkages and small volume fractions associated with any chemical transformation in a bulk material. By carrying out the chemical changes in each layer as it forms, the shrinkage can readily occur in the z-direction and the diffusion distances are all short. This also led us to realize that layers could be deposited under water as well as in air. Our deposition needle then plays much the same role as the interfacial cells in a mineralizing system. These control the structure of the composite on the millimeter scale, while structure on the scale of microns or less is determined by the physics and chemistry of the reagents.

The methods developed under the current grant will become part of the toolbox of deposition methods for SFF, allowing us to control local mineralization and to incorporate enzymatic sensors and transport polymers in soft solid materials for a range of devices and implements.

#### BIBLIOGRAPHY

1. H. S. Al-Lami, N. C. Billingham, P. D. Calvert, *Chemistry of Materials* **4**, 1200 (1992).
2. P. Calvert, M. Oner, J. Burdon, P. Rieke, K. Farmer, Block Copolymers for Biomimetic Composites, SPIE: Smart Structures and Materials Albuquerque, NM, (1993), vol. 1916, pp. 354-361.
3. M. Oner, P. Calvert, *Materials Science and Engineering C* , **2** 93-102 (1994).
4. S. Mann, et al., *Science* **261**, 1286-1292 (1993).
5. B. C. Bunker, et al., *Science* **264**, 48-55 (1994).
6. M. Kubo, W. C. Mollberg, A. B. Padias, H.K. Hall, and P. Calvert *Macromolecules* **28**, 838-843 (1995).



#### Research Personnel Supported

Postdoctoral Fellows: Mualla Oner, Jeremy Burdon, Masataka Kubo,  
Research Students: Sajiv Boggaravapu, William Mollberg (MS Degree Awarded),  
Research Scientist: Anne Padias.

#### Manuscripts Submitted

Biomimetic Processing of Ceramics for "Materials Science and Technology" Vol. 17,  
editor R. Brook., VCH Publishers

Biomimetic Inorganic Organic Composites for "Biomimetic Approaches in Materials  
Chemistry" editor S. Mann, VCH Publishers

Biomimetic Ceramics and Hard Composites for "Design and Processing of Materials by  
Biomimicking" editors I.A.Aksay and M. Sarikaya, American Institute of Physics

#### Manuscripts Published

P.Calvert, "Biosynthetic and biomimetic materials" Encyclopedia of Materials Science and  
Engineering, supp. 3, R.W.Cahn ed. Pergamon, Oxford, 1993 pp.1523-1530

J.Burdon and P.Calvert, "Control of particle size and orientation during *in situ* precipitation  
of oxides in polymers" Mat.Res.Soc.Symp. 286 315-320 (1993)

M. Kubo, W.C. Mollberg, A.B. Padias and H.K. Hall, "Solubilization of peptides in water  
and hexane: Synthesis of peptide-terminated poly(tert-butylacrylate) and poly(acrylic acid)  
via living anionic polymerization." Macromolecules (1995) 28 838-843

P.Calvert, M.Oner, J.Burdon, P.C.Rieke, K.Farmer, "Block copolymers for biomimetic  
composites" SPIE 1916 354-361 (1993)

M.Oner and P. Calvert, "Influence of polymer architecture on crystal growth inhibition"  
PMSE Preprints 69 166-7 (1993)

"Terminal-functionalized poly-t-butyl acrylates via living anionic polymerization" MS  
Thesis William Mollberg

M. Oner and P. Calvert "The effect of architecture of acrylic polyelectrolytes on inhibition  
of oxalate crystallization" Mater. Sci. Eng. C. 2 93-102 (1994)

Paul Calvert "Biomimetic mineralization: processes and prospects" Mat. Sci. Eng. C1  
(1994) 69-74

J.E.Mark and P.D.Calvert "Biomimetic, hybrid and in situ composites" Mater. Sci Eng. C.  
1 (1994) 175-186

P.Calvert "Intelligent composite materials by *in situ* precipitation" Proceedings of the  
Second International Conference on Intelligent Materials, C.A.Rogers and G.G.Wallace

eds, Technomic Press Lancaster PA, 1994 pp. 259-264

P. Calvert "Strategies for Biomimetic Mineralization" *Scripta Met.* 31 977-982 (1994)

P. Calvert and J. Burdon "Bone as a nanocomposite material" *ACS PMSE Preprints* 70 224-225 (1994)

P.D. Calvert "Polymers for new materials" *Polymer* 35 4484-4488 (1994)

J. Burdon, J. Szmania, P. Calvert, "Biomimetic composites" *Materials Research Society Symposium Proceedings* **1994**, 351, 103-108 (1994).

P. Calvert, "Precipitation in and on polymers" *Mater. Res. Soc. Symp. Proc.*, **330**, 79-88 (1994).

#### Presentations

In addition this work was presented in seminars at US Army Natick (twice), Wright Patterson AFB, Hoechst-Celanese, Dow Chemical Co., 3M, Sandia National Labs., Universities of Delaware, Minnesota and Cincinnati, Case Western Reserve University, Courtaulds Plc, Swedish Academy of Sciences.

#### No reportable inventions